

## Optimization of magnetic arc oscillation process parameters on mechanical properties of AA 5456 Aluminum alloy weldments

A. Kumar<sup>a,\*</sup>, P. Shailesh<sup>b</sup>, S. Sundararajan<sup>c</sup>

<sup>a</sup> Department of Mechanical Engineering, National Institute of Technology, Warangal, Andhra Pradesh 506 004, India

<sup>b</sup> Department of Mechanical Engineering, Osmania University, Hyderabad 500 007, India

<sup>c</sup> Scientist 'G', Defence Research and Development Laboratory, Hyderabad 500 028, India

### ARTICLE INFO

#### Article history:

Received 17 November 2007

Accepted 16 April 2008

Available online 26 April 2008

#### Keywords:

D. Welding

E. Mechanical properties

F. Microstructure

### ABSTRACT

The present work pertains to the improvement of mechanical properties of AA 5456 Aluminum alloy welds through magnetic arc oscillation process. Taguchi method was employed to optimize the magnetic arc oscillation welding process parameters of non-heat treatable AA 5456 Aluminum alloy welds for increasing the mechanical properties. The same optimum condition was observed in all the properties. Regression models were developed. The effect of welding current, welding speed, amplitude and frequency on mechanical properties was also studied. Analysis of variance was employed to check the adequacy of the developed models. Microstructures of all the welds were studied and correlated with the mechanical properties.

Crown Copyright © 2008 Published by Elsevier Ltd. All rights reserved.

## 1. Introduction

Al–Mg alloys are extensively used in defence and aerospace applications. Tungsten inert gas (TIG) welding is an arc welding process that produces coalescence of metals by heating them with an arc between a non-consumable electrode and the base metal. TIG welding process [1] is generally used for welding of Al–Mg alloys. The initial strength of the non-heat treatable aluminum alloys depends primarily upon the hardening effect of alloying elements such as silicon, iron, manganese and magnesium [2]. These elements increase the strength either as dispersed phase or by solid solution strengthening. The welding of non-heat treatable aluminum alloys typically have distinct effects when the heat input is increased, i.e. the width of the heat affected zone (HAZ) is increased and the minimum reduction in the mechanical properties are observed. Alloys 5XXX series with more than 3.0% magnesium are not recommended for elevated temperatures above 150 °F because of their potential for sensitization and subject susceptibility to stress corrosion cracking [3]. The minimum HAZ strength approximates to that of the annealed parent metal regardless of the starting temperature.

During welding, vaporization of alloying elements like magnesium can occur and this vaporization loss of any alloying elements can influence the mechanical properties of the welded joints by affecting the chemistry of the weld pool. The gas tungsten arc weld-

ing (GTAW) and gas metal arc welding (GMAW) welding processes are very often used for welding of these alloys. However, GTAW process is generally preferred because it produces a very high quality welds. Distortion is the major problem in welding of thin sections. However, the distortion is controlled in pulsed and magnetic arc oscillation GTAW process. Metallurgical advantages of pulsed and magnetic arc oscillation welds that are frequently reported in the literature includes grain refinement in the fusion zone, reduced width of HAZ, less distortion, control of segregation, reduced hot cracking sensitivity and reduced residual stresses [4–6].

The purpose of the present investigation is to optimize the magnetic arc oscillation welding process parameters for increasing the mechanical properties using Taguchi method. Taguchi method is a systematic approach to design and analyze experiments for improving the quality characteristics. Taguchi method [7–10] permits evaluation of the effects of individual parameters independent of other parameters, and also of their interactions on the identified quality characteristics, i.e. ultimate tensile strength, yield strength, hardness, etc. Nowadays, Taguchi method has become a practical tool for improving the quality of the output without increasing the cost of experimentation by reducing the number of experiments.

Welds are made with the use of obtained optimum condition, and these welds are subjected to cold planishing process. The roll planishing (Make: Jetline) is an effective process in which weld is passed between two steel rollers. During the planishing operation, the internal stresses which are induced during welding are relieved and the grains are deformed. Hence, the mechanical properties of the welds have been improved.

\* Corresponding author. Tel.: +91 9885055026 (P), +91 08702564888 (O); fax: +91 08702564320.

E-mail address: [adepukumar7@yahoo.co.in](mailto:adepukumar7@yahoo.co.in) (A. Kumar).

## 2. Scheme of investigation

In order to maximize the quality characteristics, the present investigation has been made in the following sequence:

- Selection of base material and filler material.
- Identify the important magnetic arc oscillation welding process parameters.
- Find the upper and lower limits (i.e. range) of the identified process parameters.
- Select the orthogonal array (Design of matrix).
- Conduct the experiments as per the selected orthogonal array.
- Record the quality characteristics (i.e. Mechanical properties).
- Find the optimum condition for maximizing the mechanical properties.
- Conduct the confirmation test.
- Develop the regression models to predict the mechanical properties within the selected range.
- Identify the significant factors.
- Check the adequacy of the developed models.

### 2.1. Selection of base material and filler material

The base material employed in this study is 2.14 mm thick Al–Mg Aluminum alloy welded with 5356 filler material. The chemical composition of the base material and filler material are shown in Table 1. The selection of the filler material is based on the mechanical properties and resistance to cracking in the weld [2].

### 2.2. Identify the important magnetic arc oscillation welding process parameters

From the literature [5,11] and previous work done [10,12], the most important process parameters which are having greater influence on the weld bead geometry and fusion zone grain refinement of magnetic arc oscillation GTAW welding process have been identified. They are: welding current, welding speed, amplitude and frequency.

### 2.3. The working range of the process parameters

A large number of trials have been conducted by varying one of the process parameters and keeping the others constant. The working range of welding current, welding speed, amplitude and frequency have been explored by inspecting bead appearance and the full penetration. The working range of the process parameters selected under the present study and the constant process parameters are shown in Tables 2 and 3, respectively.

### 2.4. Selection of orthogonal array

Number of process parameters are considered under this study is four and the level of each parameter is two. The degrees of freedom of all the four parameters and their interactions are seven.

**Table 1**

Chemical composition of the base material and filler material (wt%)

	Mg	Si	Cu	Cr	Mn	Zn	Ti	Fe	Al
Al–Mg (AA 5456 Aluminum alloy) (Base material)	5.3	0.3	0.1	0.35	0.65	0.10	0.20	0.40	Balance
5356 Alloy (Filler material)	5.0	–	–	0.12	0.12	–	0.13	–	Balance

**Table 2**

Working range of the process parameters

Symbol	Process parameter	Units	Lower level (1)	Higher level (2)
C	Welding current	Amps	80	100
S	Welding speed	mm/min	210	230
A	Amplitude	mm	0.3	0.6
F	Frequency	Hz	2	6

**Table 3**

Constant process parameters

Process parameter	Constant value
Shielding gas flow rate (L/min)	10
Purging gas flow rate (L/min)	5
Filler rod diameter (mm)	1.6
Electrode material	98% W + 2% Zr
Electrode diameter (mm)	3.15
Pulse ratio (%)	50
Pulse on time (%)	50

Hence, L8 ( $2^7$ ) orthogonal array is selected. Each trial was repeated twice to reduce the noise/error effects. The selected orthogonal array was presented in Table 4.

### 2.5. Conduct the experiments as per the selected orthogonal array

The base metal sheets of dimension 250 mm × 150 mm × 2.14 mm have been prepared and butt joints were made using the experimental layout shown in Table 4. An automatic TIG welding machine has been employed for conducting the welding experiments. Prior to welding, the base metal sheets were pickled with a solution of NaOH and HNO<sub>3</sub>, wire brushed, and degreased using acetone and finally preheated to 100 °C. The sheets to be welded were kept on steel backing bar and ends were clamped to maintain the alignment and gap. Purging is provided at the bottom of the sheets. The same argon gas has been used for shielding as well as purging. The weld joint is completed in single pass.

### 2.6. Record the quality characteristics (i.e. Mechanical properties)

Specimens for tensile testing were taken at the middle of all the joints and machined to ASTM E8 standards [13]. The configuration of specimen is used under tensile testing is shown in Fig. 1. Tensile test was conducted using computer controlled universal testing machine (Make: Shimadzu, Model: AUTOGRAPH) with a cross head speed of 0.5 mm/min. The entire welded specimens were failed in the weld region. The ultimate tensile strength of the weld joint is the strength of the weld.

Specimens for metallographic studies and micro hardness tests (15 mm width) were considered at the middle of all the joints. The specimens were suitably sectioned, mounted, mechanically polished according to standard metallographic procedures and are etched using modified Keller's reagent (2 ml HF, 3 ml HCl, 20 ml

**Table 4**

Experimental lay out L8 ( $2^7$ ) orthogonal array

Exp. no.	C	S	C × S	A	C × A	S × A	F
Mm1	1	1	1	1	1	1	1
Mm2	1	1	1	2	2	2	2
Mm3	1	2	2	1	1	2	2
Mm4	1	2	2	2	2	1	1
Mm5	2	1	2	1	2	1	2
Mm6	2	1	2	2	1	2	1
Mm7	2	2	1	1	2	2	1
Mm8	2	2	1	2	1	1	2

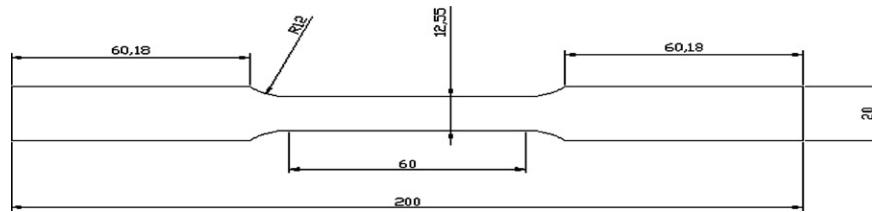


Fig. 1. Configuration of Plain tensile test specimen.

$\text{HNO}_3$  and 175 ml  $\text{H}_2\text{O}$ ). Microstructures were observed and recorded using an optical microscope. Micro hardness tests were carried out on the welded samples with a load of 15 g and a duration of 15 s using a Vickers digital micro hardness tester (make: Shimadzu, model: HMV-2000). The micro hardness was measured at an interval of 0.5 mm across the weld, 1 mm across the heat affected zone and 1.5 mm across the unaffected base metal. The schematic sketch of the hardness survey is shown in Fig. 2. The hardness distribution across the weld is shown in Fig. 3.

The quality characteristics, i.e. Ultimate tensile strength, Yield strength, Percent elongation and hardness of the weldments were evaluated for all the trails and are presented in Table 5.

#### 2.7. Find the optimum condition for maximizing the mechanical properties and conduct the confirmation test

The optimization of process parameters using Taguchi method [9–10] permits evaluation of the effects of individual parameters independent of other parameters, and also of their interactions on the identified quality characteristics, i.e. ultimate tensile strength (UTS), yield strength, percent elongation and hardness. The statistical analysis of variance (ANOVA) was carried out. Based

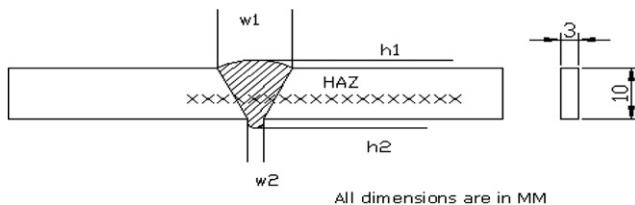


Fig. 2. Schematic sketch of hardness measurement in transverse to the weld.

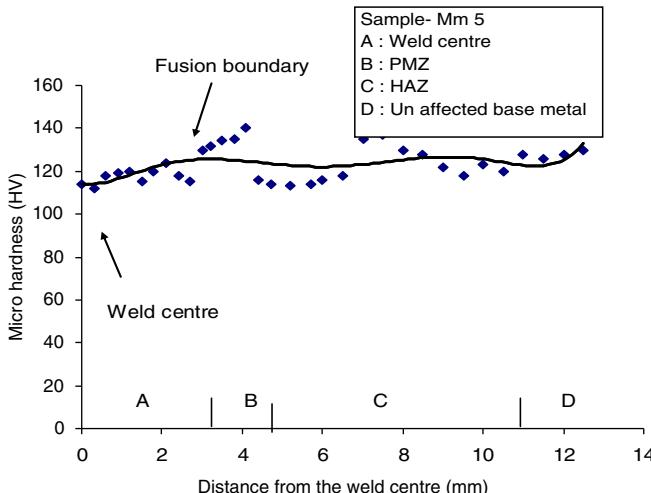


Fig. 3. Micro hardness survey in transverse to the weld direction of AA 5456 weld (Sample – Mm5).

Table 5

Mechanical properties of magnetic arc oscillation AA 5456 Aluminum alloy weldments

Specimen ID	UTS (MPa)		Yield strength (MPa)		Percent elongation		Micro hardness (HV)	
	Trail 1	Trail 2	Trail 1	Trail 2	Trail 1	Trail 2	Trail 1	Trail 2
Mm1	275	280	185	190	12	12.5	110	105
Mm2	265	260	168	176	10	10.5	102	100
Mm3	300	305	200	205	14	13.5	120	121
Mm4	270	275	175	184	10	10	101	103
Mm5	290	295	195	200	13	12.5	111	115
Mm6	265	280	180	176	11	11.5	106	108
Mm7	290	285	190	195	12	12.5	110	110
Mm8	270	280	175	180	11	11.5	109	106
Base material	325	320	228	218	18	17.5	125	120

on the ANOVA, the contribution of each process parameter and their interaction in influencing the quality characteristic is evaluated. The ANOVA also provides an indication of which process parameters are statistically significant. The optimum process parameter combination is predicted and the optimum results are presented in Table 6. The same optimum combination is observed in all the quality characteristics. For validations of the optimum results, experiments are conducted as per the optimum conditions and mechanical properties are evaluated and the average results are presented in Table 7. It is observed that, experimental values were closer to the optimum values.

#### 2.8. Develop the regression models

The responses  $Y$  such as ultimate tensile strength, yield strength, percent elongation and hardness are the function of welding current, welding speed, amplitude and frequency. The response function can be expressed as

$$Y = f(\text{welding current, welding speed, amplitude, frequency})$$

$$Y = f(C, S, A, F)$$

The regression model selected includes the effects of main factors and first order interactions of all the factors. It is the part of power series of polynomial and expressed as

$$Y = b_0 + b_1(C) + b_2(S) + b_3(A) + b_4(F) + b_{12}(CS) + b_{13}(CA) + b_{23}(SA)$$

Table 6  
Optimum values of the quality characteristics

Quality characteristics	Optimum condition	Optimum value
UTS (MPa)	$C_1S_2A_1F_2$ , i.e. Welding current at level 1 (80 A),	300
Yield strength (MPa)	Welding speed at level 2 (230 mm/min),	205
Percent elongation	Amplitude at level 1 (0.4 mm) and Frequency at level 2 (6 Hz)	14
Hardness (HV)		125

**Table 7**  
Validation of the optimum results

Quality characteristics	Optimum condition	Optimum value	<sup>a</sup> Experimental value
UTS (MPa)	C <sub>1</sub> S <sub>2</sub> A <sub>1</sub> F <sub>2</sub>	300	298.25
Yield strength (MPa)		205	203.58
Percent elongation		14	13.56
Hardness (HV)		125	124.25

<sup>a</sup> Average of three values.

**Table 8**  
Regression equations for the mechanical properties of the weldments

S.No.	Response	Regression equation	Coefficient of correlation
1	Ultimate tensile strength	$Y = 280.31 + 1.56 C + 4.06 S - 9.69 A + 2.81 F - 4.69 CS + 1.56 CA - 0.94 SA$	0.91
2	Yield strength	$Y = 185.88 + 0.50 C + 2.13 S - 9.13 A + 1.50 F - 3.50 CS + 0.50 CA - 0.38 SA$	0.92
3	Percent elongation	$Y = 11.47 + 0.59 C - 0.09 S - 0.72 A + 0.47 F - 0.22 CS - 0.47 CA + 0.28 SA$	0.97
4	Hardness	$Y = 108.56 + 0.81 C + 1.44 S - 4.19 A + 1.94 F - 2.06 CS + 2.06 CA - 1.06 SA$	0.94

Where C = Welding current, S = welding speed, A = Amplitude and F = Frequency.

where  $b_0$  is the average of responses,  $b_1, b_2, \dots$  and  $b_{23}$  are the regression coefficients (i.e.  $b_k$ ) that depend on respective main and interaction factors which are calculated by using the following expression [14–15]:

$$b_k = \frac{\sum_{i=1}^N X_{ik} Y_k}{N}, \quad k = 0, 1, 2, \dots, n \quad (1)$$

where  $X_{ik}$  is the value of factor or interaction in coded form,  $Y_k$  is the output response (Ultimate tensile strength, yield strength, percent elongation and micro hardness),  $N$  is the number of observations and  $n$  is the number of coefficients of the model. The coefficients

of the variables and their interactions are computed using the above relationship.

### 2.9. Identify the significant factors

Analysis of variance (ANOVA) is applied to find out the significance of main factors and their interactions. In addition the *F*-test can also be used to determine which welding process parameter has significant effect on the response (i.e. ultimate tensile strength, yield strength, percent elongation and hardness). Usually, the change of the welding process parameter has significant effect on the response when the *f*-ratio is large. It is found that the coefficients of the variables and their interactions are significant.

### 2.10. Check the adequacy of the developed models

Coefficient of correlation '*r*' is used to find how close the predicted and experimental values lie and it is calculated using the following expression:

$$R^2 = \sum (Y_p - Y_a)^2 / \sum (Y_e - Y_a)^2 \quad (2)$$

where  $Y_p$  is the predicted (using the above model);  $Y_e$  is the experimental value;  $Y_a$  is the average of experimental values. The developed regression equations and the corresponding coefficients of correlation are presented in Table 8. It is observed that, the coefficients of correlation of the entire developed model are found to be higher values. Hence the developed models are significant.

### 2.11. Validations of the developed models

A few numbers of observations are taken under different sets of parameters within the limits investigated and the corresponding estimated values are determined by the use of developed model. The results of predicted and experimental values are shown in Table 9. It is observed that, the percentage error is found to be very small. Hence the developed model is so adequate within the selected variables.

**Table 9**  
Validation of the process models of magnetic arc oscillation TIG welds of AA 5456 Aluminum alloy

Sl. no.	Experimental condition				Process model value	Experimental value	Percentage deviation
	Welding current	Welding speed	Amplitude	Frequency			
<i>(a) UTS (MPa)</i>							
1	80	210	0.4	4	282.64	276.00	2.34
2	80	210	0.4	6	284.05	310.00	9.14
3	80	210	0.5	6	279.52	285.00	1.94
4	80	210	0.6	6	275.00	280.00	1.18
5	80	210	0.4	2	281.21	280.00	0.45
<i>(b) Yield strength (MPa)</i>							
1	80	210	0.4	4	181.76	185.00	1.78
2	80	210	0.4	6	186.51	205.00	9.99
3	80	210	0.5	6	182.00	190.00	4.39
4	80	210	0.6	6	172.50	195.00	13.40
5	80	210	0.4	2	185.01	185.00	0.01
<i>(c) Percent elongation</i>							
1	80	210	0.4	4	11.98	11.00	8.10
2	80	210	0.4	6	12.32	13.00	5.51
3	80	210	0.5	6	11.48	12.00	4.52
4	80	210	0.6	6	10.75	13.00	2.09
5	80	210	0.4	2	11.75	11.00	6.18
<i>(d) Micro hardness (HV)</i>							
1	80	210	0.4	4	108.34	107.00	1.24
2	80	210	0.4	6	108.97	121.00	11.03
3	80	210	0.5	6	107.32	115.00	7.15
4	80	210	0.6	6	105.50	114.00	8.05
5	80	210	0.4	2	107.15	107.00	0.01

### 3. Planishing

The roll planishing (Make: Jetline) is an effective process in which weld is passed between two steel rollers. The optimum pressure is applied between the rollers is about 2 bar and the optimum speed of 30 mm/min so that weld bead is pressed and there is no top and bottom reinforcement. During the planishing operation, the internal stresses which are induced during the welding are relieved and the grains are deformed [16]. Hence, mechanical properties are improved. The schematic sketch of roll planishing process is shown in Fig. 4.

Welds are made with the use of obtained optimum condition, and these welds are subjected to cold planishing process. Mechanical properties are evaluated and compared with these results to unplanned condition. Mechanical properties of weldments before and after planishing are presented in Table 10.

### 4. Discussion

During tensile tests all the welded specimens were failed within the weld region. Thus it may be assumed that the ultimate tensile strength is the strength of the weld. Magnetic arc oscillation welds

**Table 10**


Comparison of mechanical properties of magnetic arc oscillation AA 5456 Aluminum alloy weldments before and after planishing

Quality characteristics	Optimum condition	Before planishing	After planishing
UTS (MPa)	C <sub>2</sub> S <sub>1</sub> A <sub>2</sub> F <sub>2</sub>	298.25	312.25
Yield strength (MPa)		203.58	214.25
Percent elongation		13.56	15.26
Hardness (HV)		124.25	126.24

have shown fine grain structure compare to the continuous and pulsed welds is due to thermal disturbances and increase in welding speed.

In general, hardness in the fusion zone is lowest due to the as-cast nature of the microstructure, which is characterised by the coarse dendrite grains, interdendritic segregate phases, and the lack of strengthening phase. Hardness is higher compared to the pulsed and continuous welds and this could be due to refinement of grain structure and low segregation of phases [17].

The portion of the HAZ close to the weld is harder than the rest of the HAZ, but still softer than the base metal [18]. It is due to fact that, weldment was subjected to sufficient heat for a reasonable

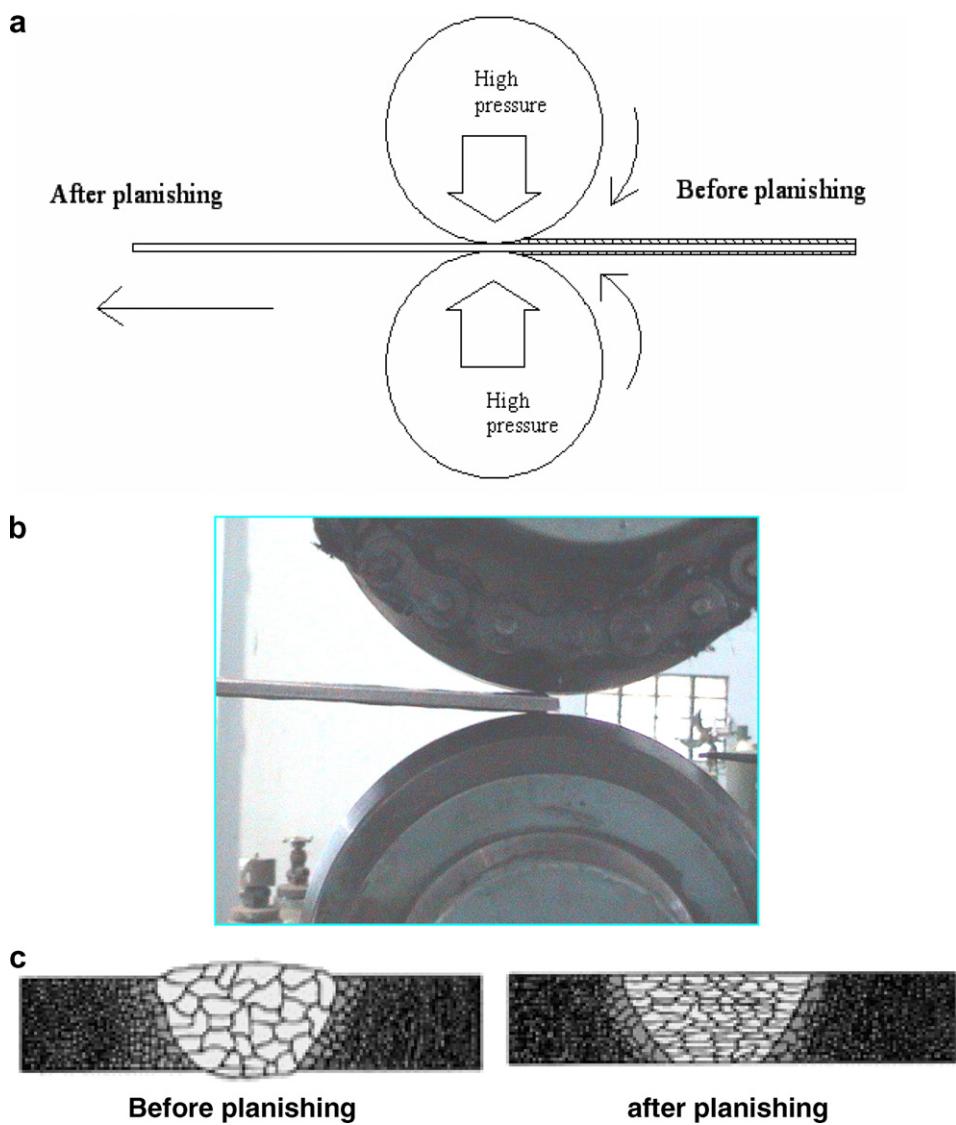

**Fig. 4.** Planishing process (a) Schematic sketch of roll planishing process, (b) closed view, during operation and (c) comparison of microstructure before and after planishing.

amount of solutionizing and fast enough cooling rate to be quenched and produce a some what super saturated solid solution. Very fine precipitates (i.e.  $Mg_2Al_3$ ) could have formed during cooling or during natural aging, resulting in a local hardness peak in close to the fusion boundary.

The microstructures at the weld centre of magnetic arc oscillation welds using the experimental layout are shown in Fig. 5. From

these figures, it is evident that, the samples welded by using the condition, i.e. Mm3 (welding current – 80 A, welding speed – 230 mm/min, amplitude – 0.3 mm, and frequency – 6 Hz) resulted in fine equiaxed grains compare to other conditions. It is also observed that, fine interdendritic network of aluminum with much of the  $Mg_2Al_3$  eutectic (dark) precipitates near grain boundaries. It is evident that, at higher frequency, the thermal and mechanical

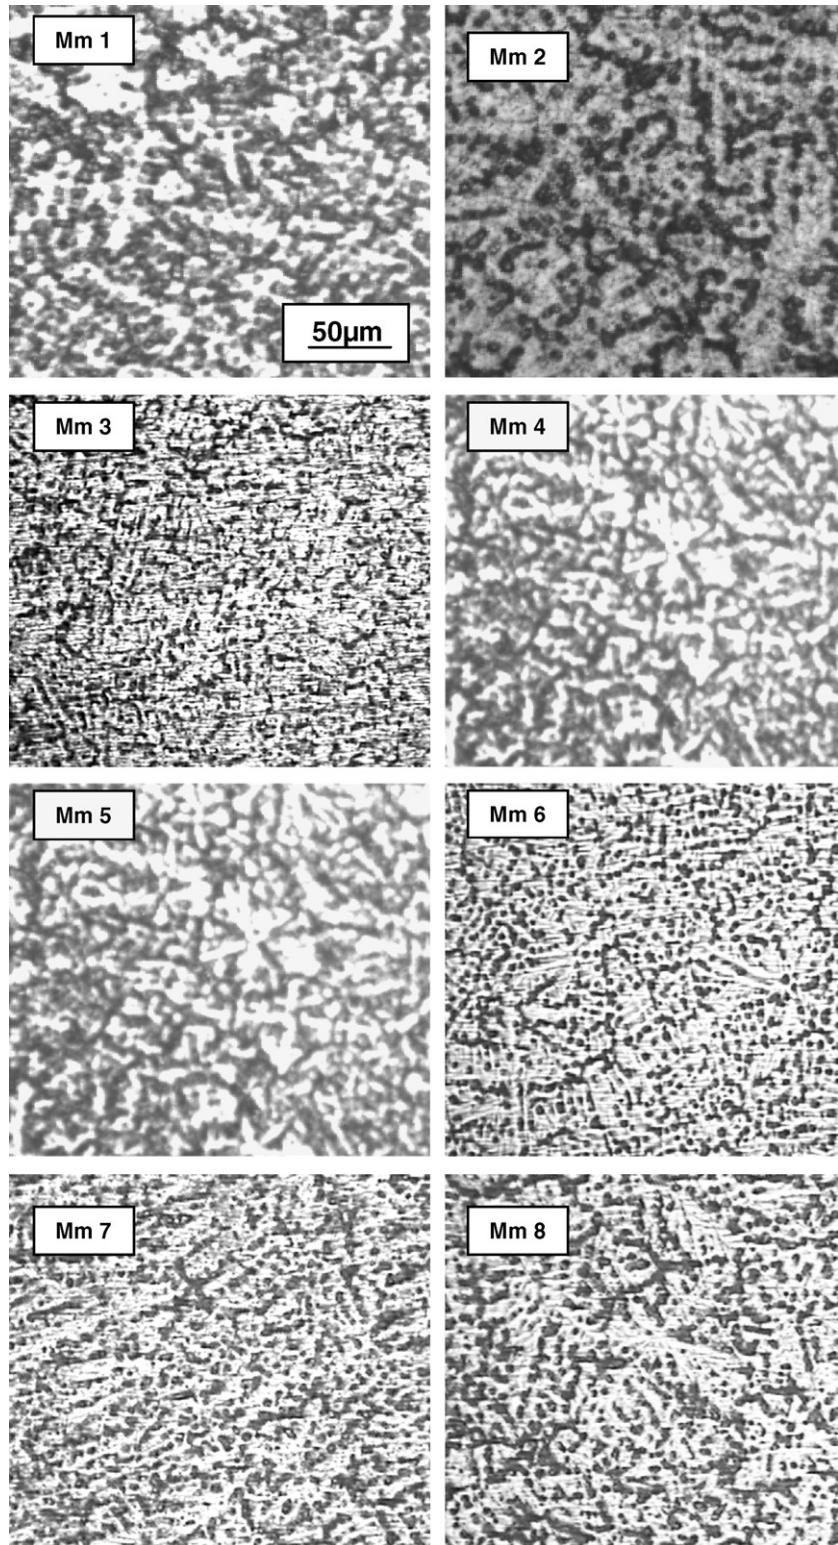



Fig. 5. Microstructures at the weld centre of magnetic arc oscillation TIG welds.

disturbances might be more. This is due to fact that the weld pool resonant frequency is closer to the experimental frequency of operation, i.e. at 6 Hz. Similar trends have been observed in the literature [11].


The microstructure observation of the condition set, i.e. Mm6 (welding current – 100 A, welding speed – 210 mm/min, amplitude – 0.6 mm and frequency – 2 Hz) is resulted in coarse grain structure. It might be expected that the thermal and mechanical disturbances would be less at lower frequencies. From the observation of the weld microstructures, it is clear that, the combination of

welding current, welding speed, amplitude and frequency resulted in fine equiaxed grain structure.


The aim of this paper is to emphasize on the quality characteristic with minimum number of experiments for the process parameters carried out for which Taguchi method is adopted. The same optimum condition was observed for all the quality characteristics. The percentage contribution for the process parameters and of their interactions on the quality characteristics are presented in graphical form (Fig. 6). From the Fig. 6a–d, it is evident that, percent contribution of amplitude is shown higher values in all the

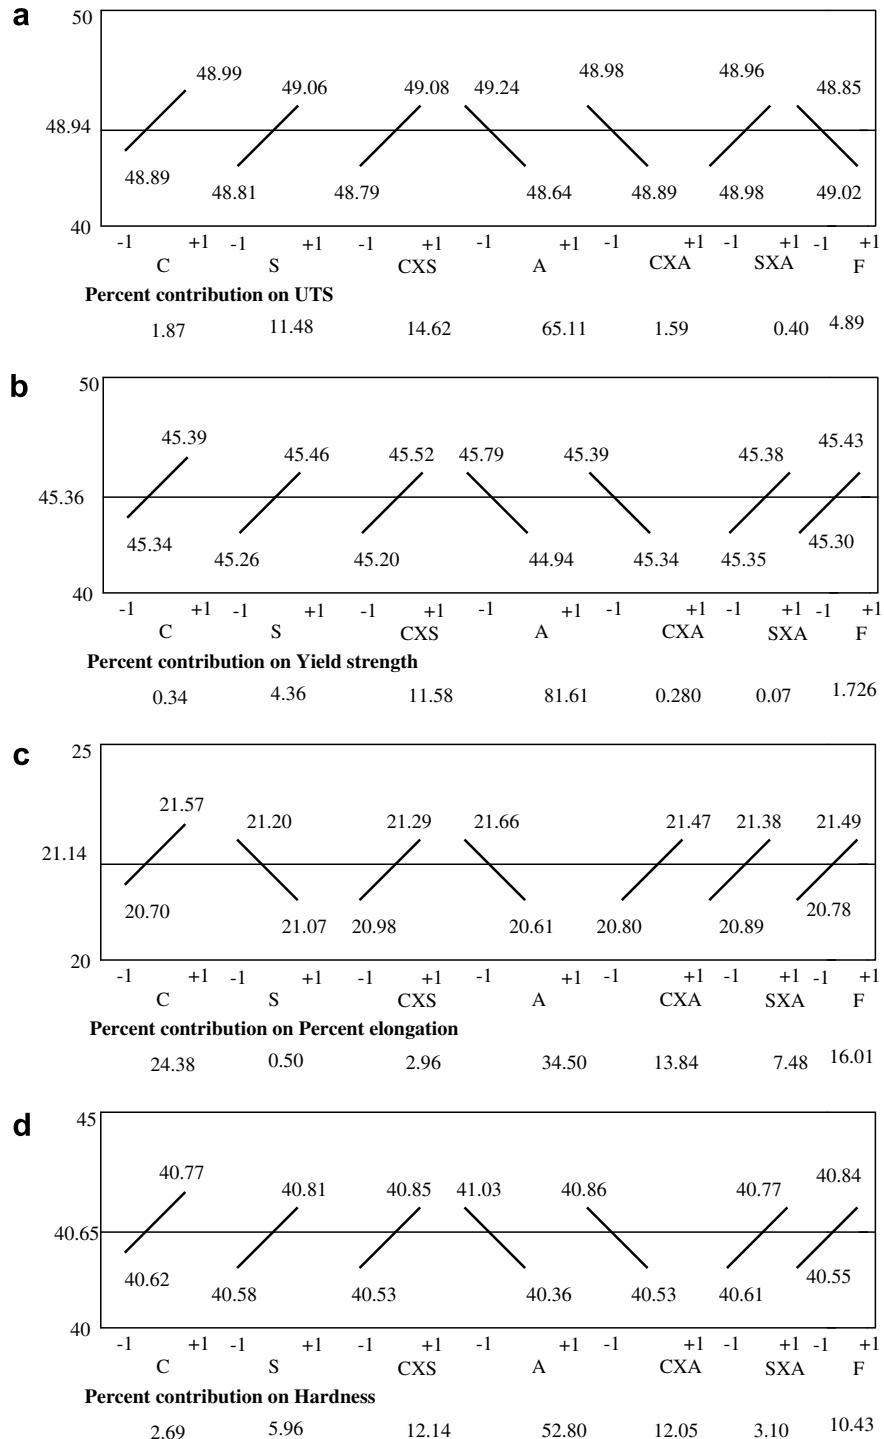


**Fig. 6.** Graphical representation of S/N ratio and percent contribution of parameters and their interactions: (a) dilution, (b) NTS, (c) impact toughness and (d) micro hardness.

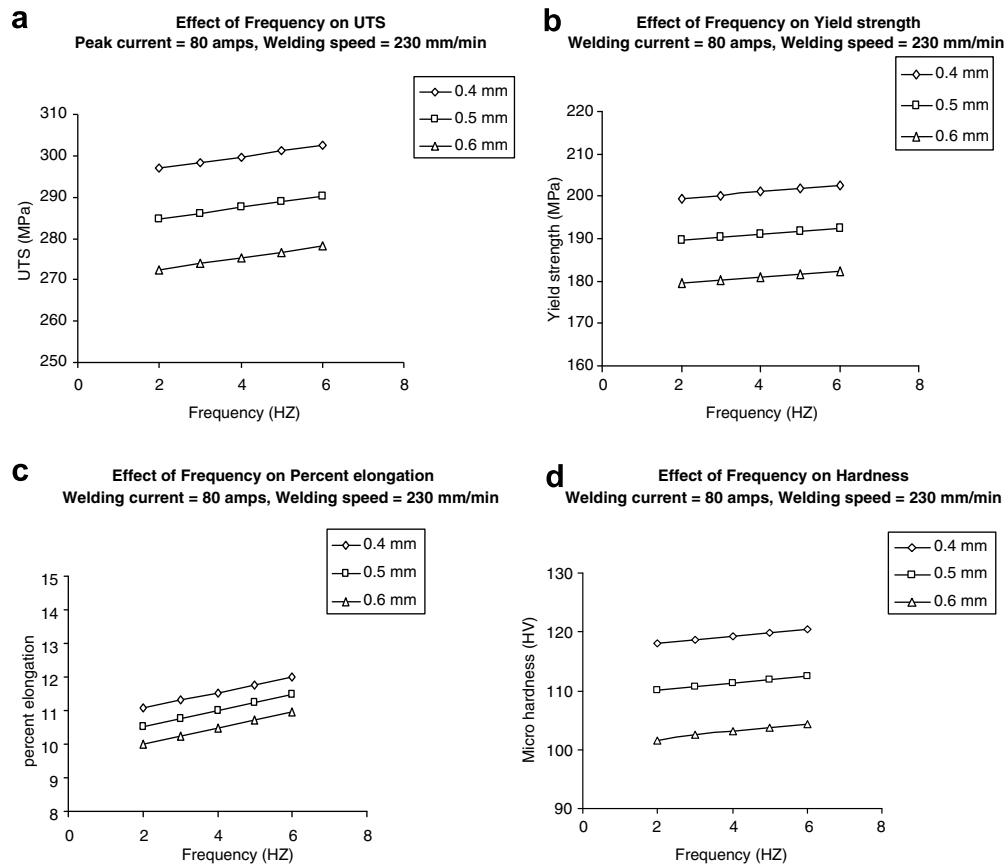

**Fig. 7.** Effect of frequency on the responses of magnetic arc oscillation welds of AA 5456 Aluminum alloy: (a) UTS, (b) yield strength, (c) percent elongation and (d) micro hardness.

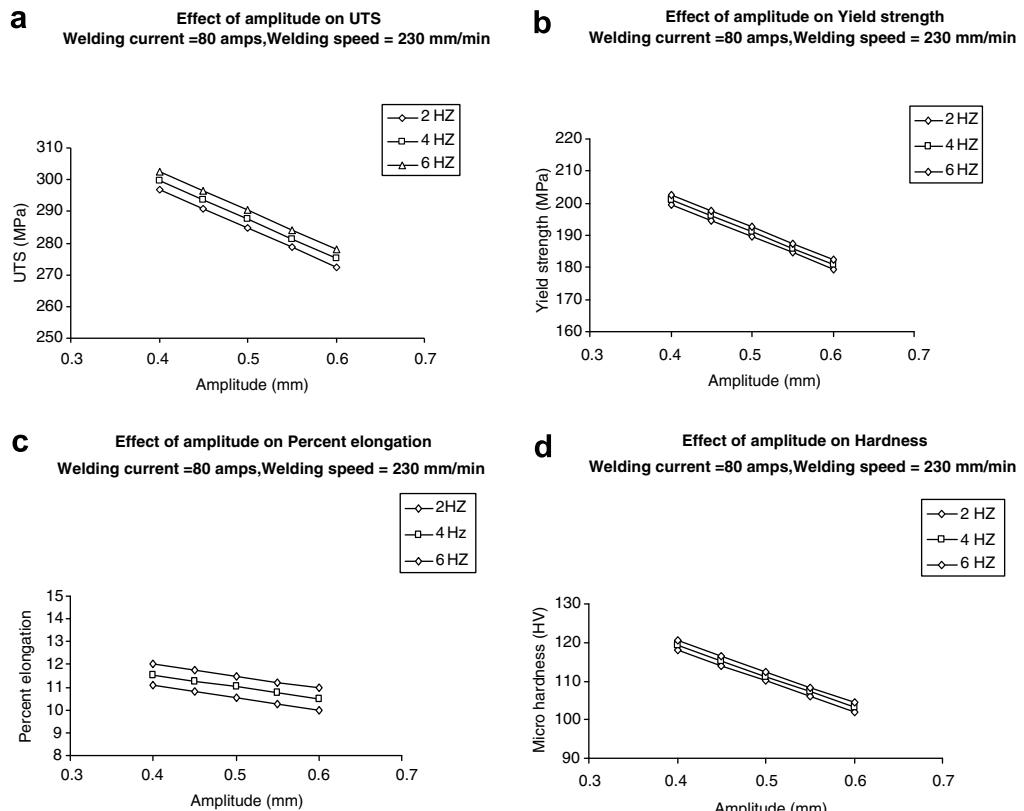

**Fig. 8.** Effect of amplitude on the responses of magnetic arc oscillation welds of AA 5456 Aluminum alloy: (a) UTS, (b) yield strength, (c) percent elongation and (d) micro hardness.

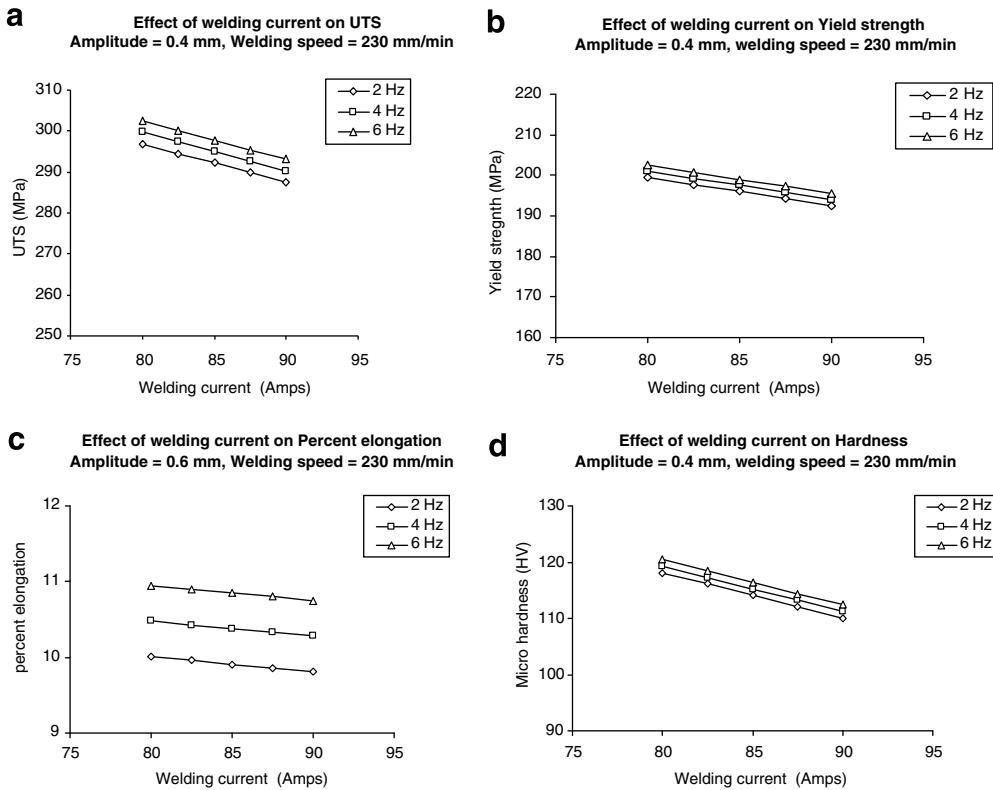

**Fig. 9.** Effect of welding current on the responses of magnetic arc oscillation welds of AA 5456 Aluminum alloy: (a) UTS, (b) yield strength, (c) percent elongation and (d) micro hardness.

properties. Hence, the effect of amplitude is more influence on the mechanical properties welds. And it is also observed that, frequency and interaction between welding current and welding speed were significant.

Mathematical models have been developed and written in MATLAB. The developed programs have been used to estimate the mechanical properties of AA 5456 Aluminum welds. Predicted values are plotted as graphs and presented in Figs. 7–9. The plotted graphs can be effectively used to understand the effect of amplitude and frequency, amplitude and welding current on mechanical properties of AA 5456 Aluminum alloy welds.

## 5. Conclusions

The influence of magnetic arc oscillation parameters such as welding current, welding speed, amplitude, and frequency on mechanical properties such as ultimate tensile strength (UTS), yield strength, percent elongation and hardness of AA 5456 Aluminum alloy have been analyzed in detail and the following conclusions have been obtained.

The same optimum combination (i.e.  $C_2S_1A_2F_2$ ) is observed in all the mechanical properties of welds. The behavior of the welded joints at the optimum condition (i.e.  $C_2S_1A_2F_2$ ) of process parameters is attributed to increase an amount of  $Mg_2Al_3$  precipitates that are formed in the Aluminum matrix. In addition the metallographic analysis reveals fine grain structure at the weld centre resulting in high mechanical properties.

It is observed that, there is 10–15% improvement in mechanical properties after planishing. This is due to fact that, internal stresses are relieved or redistributed in the weld.

Regression equations were developed to predict the quality characteristics within the selected range of parameters.

The practical benefit this study is that, use of obtained optimum condition increases the mechanical properties and developed regression models are useful for the automation of the process.

## Acknowledgements

The authors would like to thank the authorities of DRDL, Hyderabad and NIT, Warangal for providing the facilities to carryout this work.

## References

- [1] Cary HB. Modern welding technology. (NJ): Prentice-Hall; 1989.
- [2] Davis JR. ASM specialty handbook: aluminum and aluminum alloys. Ohio: ASM International Materials Park; 1994.
- [3] Tony Anderson. The American welder-understanding aluminum alloys. Weld J 2002;81(4):77–80.
- [4] Kou S, Le Y. Nucleation mechanism and grain refining of weld metal. Weld J 1986;65(4):65–70.
- [5] Tsang, Savage. The effect of Arc oscillation in either transverse or longitudinal direction has beneficial effect on the fusion zone microstructure and tends to reduce sensitivity in hot cracking. Weld J 1971;50(11):777–86.
- [6] Madusudhan Reddy G, Gokhale AA, Prasad Rao K. Weld microstructure refinement in a 1441 grade Al-Lithium alloy. J Mater Sci 1997;32: 4117–21.
- [7] Ross PJ. Taguchi techniques for quality engineering. New York: McGraw-Hill; 1998. p. 24–98.
- [8] Montgomery, Douglas C. Design and analysis of experiments. New York: John Wiley and Sons Inc.; 1997. p. 395–476.
- [9] Madhav Phadke S. Quality engineering using robust design. (NJ): Prentice-Hall; 1989.
- [10] Kumar A, Sundarajan S. Selection of welding process parameters for the optimum butt joint strength of an aluminum alloy. Mater Manuf Process 2006;21(8):789–93.
- [11] Sunadaresan S, Janaki ram GD. Use of magnetic arc oscillation for grain refinement of gas tungsten arc welds in titanium alloys. Sci Technol Weld Join 1999;4(3):151–60.

- [12] Kumar A, Nageshwar Rao GVS, Sundarajan S. Modelling and simulation of pulsed TIG welding process of an aluminum alloy. *Int J Logic Intelligent Syst* 2007;1(1–2):85–94.
- [13] Annual Book of ASTM Standards. Philadelphia, PA: American Society for Testing of Materials; 2004.
- [14] Kempthorne. *Design and analysis of experimental design*. New York: John Wiley and Sons; 1996.
- [15] Ravindra J, Parmer RS. Mathematical model to predict weld bead geometry for flux cored arc welding. *Metal Construct* 1987;19:45–52.
- [16] Priya R, Viswanathan N, Murthy CVS, Gopalakrishna K, Prasad Rao K. Effect of planishing and scandium on AA 2014 weld metals. In: *Symposium on joining of materials*, WRI, Tiruchurapalli; 2004.
- [17] Madusudhan Reddy G, Gokhale AA, Prasad Rao K. Optimization of pulse frequency in pulsed current gas tungsten inert gas welding of aluminum lithium alloy sheets. *J Mater Sci Technol* 1998;14:61–6.
- [18] Kostrivs A, Lippold JC. A method for studying weld fusion boundary microstructure evaluation in aluminum alloys. *Weld J* 2000;79(1):1s–8s.